

QUANTUM MONTE-CARLO CALCULATIONS FOR INTEGER-DOPED FULLERIDES

ERIK KOCH^a, OLLE GUNNARSSON^b, and RICHARD MARTIN^a

^{a)} *Department of Physics and Materials Research Laboratory,
University of Illinois, Urbana, IL 61801, USA*

^{b)} *Max-Planck-Institut für Festkörperforschung, 70569 Stuttgart, Germany*

The doped Fullerides can be well described by a Hubbard model, which comprises the partly filled, threefold-degenerate t_{1u} orbital and the on-site Coulomb interaction U . The orbital degeneracy is known to shift the critical ratio U_c/W for the Mott-Hubbard transition towards larger values. This puts the half-filled alkali-doped Fullerides A_3C_{60} on the metallic side of the transition. Prompted by the recent synthesis of isostructural families of integer-doped Fullerides with different fillings, we investigate how the orbital degeneracy affects the Mott transition at integer fillings $n \neq 3$. The calculations are done by fixed-node Diffusion Monte-Carlo, using a trial function, which permits us to systematically vary the magnetic character of the system.

1 Introduction

Due to the relatively large distance between the C_{60} molecules in solid Fullerides the molecular energy levels merely broaden into narrow subbands. Doping the solid with alkali atoms has the effect of filling the subband derived from the LUMO, the t_{1u} orbital. Band structure calculations indicate that the electronic structure changes little upon doping, if the compounds retain the same crystal structure.¹ The width of the t_{1u} band should thus be fairly independent of doping, and, for the Fullerides with fcc structure exhibiting orientational disorder, is estimated to be $W \approx 0.5 \dots 0.8$ eV.² The Coulomb interaction between two electrons on the same C_{60} molecule is in the range $U \approx 1.2 \dots 1.5$ eV, and should also be quite independent of doping.³

An effective Hamiltonian for the electrons in the partially filled band is given by a multi-band Hubbard model, taking into account the hopping between the t_{1u} -orbitals on neighboring molecules and the on-site Coulomb interaction U . It turns out that, as a consequence of the three-fold degeneracy of the t_{1u} -orbital, A_3C_{60} is a strongly correlated metal, close to a Mott-transition.² Here we investigate the critical ratio U_c/W at which the metal-insulator transition takes place for the other, integer-doped Fullerides A_nC_{60} with fcc structure. Our work has been prompted by the recent synthesis of isostructural families of doped Fullerides.⁴ We give an intuitive argument for the doping-dependence of the Mott-transition, and present results of Quantum Monte-Carlo calculations indicating that the metal-insulator transition is shifted towards smaller U_c/W as one moves away from half-filling.

2 Degeneracy Enhancement

We first consider the effect of orbital degeneracy on the Mott-Hubbard transition in a highly idealized model. A system with L electrons becomes insulating when the conduction gap

$$E_g = E(L + 1) - 2 E(L) + E(L - 1) \quad (1)$$

opens. In the limit of large Coulomb interaction $U \gg t$, we can estimate the energies entering eqn. (1). For integer filling $L = n M$, where M is the number of molecules in the system, all molecules will be occupied by n valence electrons. Hopping is strongly suppressed, since it increases the energy by U . Hence for the integer filled system, to leading order in t^2/U , there is no kinetic contribution to the total energy

$$E(L) = \frac{n(n-1)}{2} M U + \mathcal{O}(t^2/U) \quad (2)$$

In contrast, the systems with $L = n M \pm 1$ electrons have an extra electron/hole that can hop without an additional cost in Coulomb energy. To estimate the kinetic contribution to the total energy, we calculate the hopping matrix-element for hopping of the extra charge to a neighboring molecule. We notice that for the non-degenerate Hubbard model a ferromagnetic arrangement of the spins is energetically favored (Nagaoka's theorem for bipartite lattices⁵). For a degenerate Hubbard model, however, the hopping matrix element is larger for an antiferromagnetic alignment of the spins on neighboring sites. In that case, as illustrated in Fig. 1, instead of only one, several equivalent electrons can hop. To estimate the matrix element for nearest-neighbor hopping, we calculate the matrix element for hopping of the extra electron/hole against a Néel state $|0\rangle$. Denoting the state with the extra charge on site i by $|i\rangle$, we find that the second moment of the Hamiltonian $\langle i|H^2|i\rangle$ is given by the number of hopping channels k times the number of (equivalent) nearest-neighbors z times the single-electron hopping matrix-element t squared. By inserting the identity in the form $\sum_j |j\rangle\langle j|$, where $|j\rangle$ denotes the state with the extra charge hopped from site i to the neighboring site j , we then find

$$\langle i|H|j\rangle = \sqrt{k} t \quad (3)$$

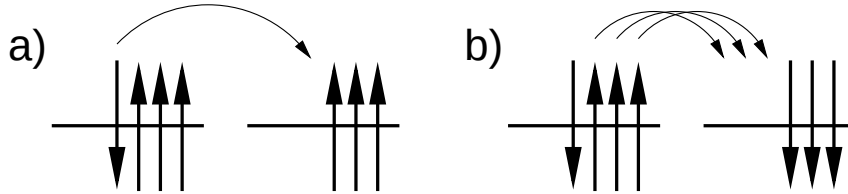


Figure 1: Illustration of how an extra electron can hop against an integer-filled background (here: degeneracy $N = 3$, filling $n = 3$). a) ferromagnetically aligned neighbor: Only one electron can hop. b) antiferromagnetically aligned neighbor: There are three hopping channels.

i.e. the hopping matrix-element is enhanced by a factor of $\sqrt{k}$ compared to the one-particle case. Taking the analogy with the one-particle problem further, we then expect the energy of the system to be lowered by $\sqrt{k}$ times half the single-electron band-width W . The gap in the limit $U \gg t$ is thus given by

$$E_g = U - \left(\sqrt{k_{L+1}} + \sqrt{k_{L-1}} \right) W/2. \quad (4)$$

Without degeneracy we have $E_g = U - W$, while for orbital degeneracy $N = 3$ we find

filling	$n = 1, 5$	$n = 2, 4$	$n = 3$
$(\sqrt{k_{L+1}} + \sqrt{k_{L-1}})/2$	$(\sqrt{2} + 1)/2 \approx 1.21$	$(\sqrt{3} + \sqrt{2})/2 \approx 1.57$	$\sqrt{3} \approx 1.73$

i.e. extrapolating the result to intermediate U , we expect that the degeneracy enhancement shifts the critical ratio U_c/W to larger values, compared to the non-degenerate case. The shift is largest for half-filling and becomes smaller as one moves away from $n = 3$. The symmetry of the result around half-filling reflects the electron-hole symmetry (we have implicitly assumed a bipartite lattice). We stress that the above argument is not rigorous, its main purpose is to give an idea of how orbital-degeneracy affects the electron dynamics.

3 Quantum Monte-Carlo Results

To investigate the doping dependence of the Mott-transition in the doped Fullerenes, we have performed Quantum Monte-Carlo calculations for fcc clusters of up to 32 molecules, using a multi-band Hubbard-Hamiltonian. The hopping integrals have been obtained from a tight-binding parameterization,⁶ while U has been varied to find the Mott-transition. The ground state energies entering in eqn. (1) have been determined by diffusion Monte-Carlo calculations using the fixed-node approximation.⁷ As trial function we have used the product of a Slater-determinant and a Gutzwiller factor. The Slater-determinant has been determined from a Hartree-Fock (HF) calculation. To allow for different magnetic characters of the trial function, we have treated the Coulomb-interaction U_0 in the HF calculation as a variational parameter.

Our results for fillings $n = 1 \dots 3$ are shown in Fig. 2. As suggested by the degeneracy argument, we find that the critical ratio decreases as we move away from half-filling. Under the caveat that the neglected effects (higher subbands, multiplet effects, electron-phonon coupling) do not change the results drastically, we can conclude that the hypothetical doped Fullerenes at low temperatures *with $Fm\bar{3}m$ structure* are strongly correlated systems with A_2C_{60} being very close to the Mott transition and A_1C_{60} possibly already being in the insulating regime.

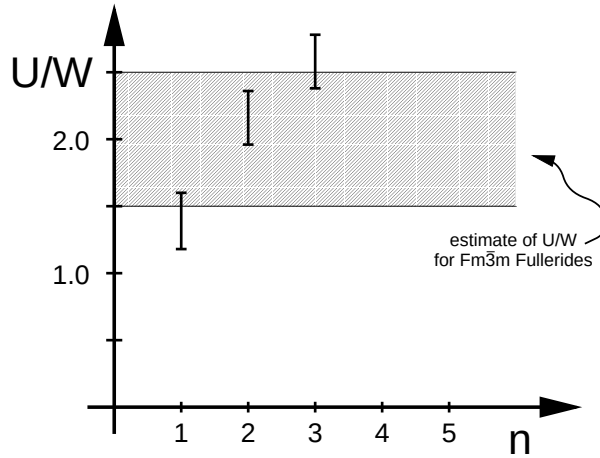


Figure 2: Estimate of the critical ratio U_c/W for a multi-band Hubbard model describing the doped Fm $\bar{3}$ m Fullerenes at integer fillings n . The bars give our estimates for U_c/W . The hatched region indicates the U/W range in which these Fullerenes are believed to lie.

Acknowledgments

This work has been supported by the Department of Energy under grant DEFG 02-91ER45539. The computations were performed on the SP2 at the Cornell Theory Center. One of the authors (E.K.) wants to thank the Alexander-von-Humboldt-Stiftung for financial support under the Feodor-Lynen-Program.

References

1. S. Erwin, in *Buckminsterfullerenes*, Eds. W.E. Billups and M.A. Ciufolini (VCH Publ., New York, 1993)
2. O. Gunnarsson, E. Koch, and R.M. Martin, *Phys. Rev. B* **54**, R11026 (1996); See also the contribution by O. Gunnarsson in this volume.
3. P.A. Brühwiler, A.J. Maxwell, A. Nilsson, N. Mårtensson, and O. Gunnarsson, *Phys. Rev. B* **48**, 18296 (1993)
4. T. Yildirim, L. Barbedette, J.E. Fischer, C.L. Lin, J. Robert, P. Petit, and T.T. Palstra, *Phys. Rev. Lett.* **77**, 167 (1996)
5. Y. Nagaoka, *Phys. Rev.* **147**, 392 (1966)
6. O. Gunnarsson, S. Satpathy, O. Jepsen, and O.K. Andersen, *Phys. Rev. Lett.* **67**, 3002 (1991);
S. Satpathy, V.P. antropov, O.K. Andersen, O. Jepsen, O.Gunnarsson, and A.I. Liechtenstein, *Phys. Rev. B* **46**, 1773 (1992)
7. D.F.B. ten Haaf, H.J.M. van Bommel, J.M.J. van Leeuwen, W. van Saarloos, and D.M. Ceperley, *Phys. Rev. B* **51**, 13039 (1995);
H.J.M. van Bommel, D.F.B. ten Haaf, W. van Saarloos, J.M.J. van Leeuwen, and G. An, *Phys. Rev. Lett.* **72**, 2442 (1994)